

FLOWCAST GRC

High Performance Multi-functional Admixture for GRC

Description

Flowcast GRC is a unique polymer plasticiser blend that has been specifically developed for use in Premix GRC. Based on a new generation dispersing agent and carefully selected polymer blends its molecular structure has been designed to promote exceptional properties.

Comprising integrated polymers, viscosity modifiers and superplasticising systems, **Flowcast GRC** offers the GRC producers enhanced strength gain, improved flexural strengths, faster demoulding and improved dry curing times than traditional GRC admixtures and polymers.

Applications

Flowcast GRC is primarily used for making free flowing premix GRC products and will allow a more controlled working life, which is enhanced by improvements in the dry curing process.

Benefits in GRC

- increased early age compressive strengths
- increased flexural strengths
- reduced shrinkage
- reduced water absorption
- eliminates waste
- lower film form temperature
- health and safety benefits
- improved surface finish

Properties

Nature	Powder
Colour	White
Bulk Density	0.600 g/cm ³
pH	-
Chloride Content	<0.10%
Na ₂ O equivalent	<1.00%

Addition Rates

Dosage rate will be dependent on the mix design, the production process, the types of aggregates and the desired finish but is typically:

180-250 grams per 25 kg cement.

For sprayed GRC applications please use **SprayCast GRC** which has an increased open life.

Standards

Flowcast GRC is produced in accordance with the ISO 9001 Quality Management Standard and the ISO 14001 Environmental Management Standard.

Testing

Flowcast GRC has been independently tested to BS EN 1170 parts 5-8.



O|S|C|R|E|T|E
construction products




FLOWCAST GRC

High Performance Multi-functional Admixture for GRC

Technical

The large area under the load-deflection curve indicates greater resilience, ductility (crack control) and impact resistance of the GRC material made with the Flowcast admixture. The more mature matrix at 28 days age provides greater efficiency of fibre reinforcement leading to higher post-cracking flexural strengthening. The glass fibre reinforcement imparts considerable ductility (crack control) and flexural strengthening to the brittle matrix composite, making it suitable for many applications in buildings. Producers have more latitude to modify concrete mix design, save costs and be more innovative with design possibilities when using a Flowcast modified GRC. Greater ductility means the potential for lighter, stronger components which are easier to handle and are less prone to damage in transit and during installation on-site.

The pre-weighed 250g packing provides improved accuracy of dosing, reduced wastage and better inventory control together with a generally cleaner, safer working environment by virtue of the reduction in occurrence of liquid spills and consequent slip hazards.

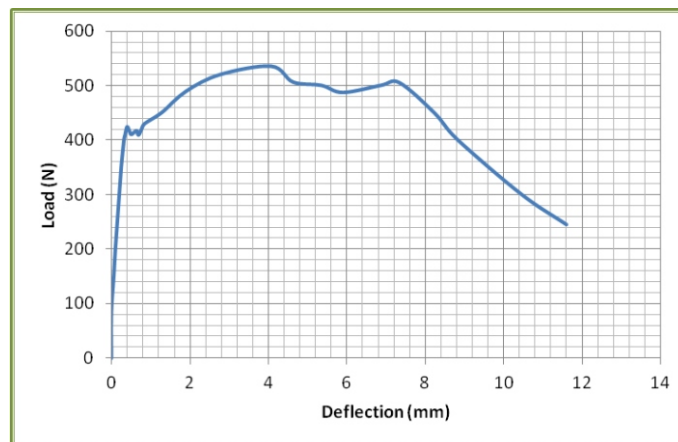

		Premix	FlowCast	Test Method
Dry Density	kg/m ³	1900 ⁺³⁰⁰ / ₋₂₀₀	2120	EN 1170-6
<u>28 day bending strength</u>				
LOP	MPa	7 +/- 2	8.93	EN 1170-5
MOR	MPa	9 +/- 3	11.44	EN 1170-5
Water Absorption at 24 hours	%	11 +/- 3	7.18	EN 1170-6
Shrinkage	mm/m	1.2 +/- 0.3	0.928	EN 1170-7
Swelling	mm/m	1.2 +/- 0.3	0.709	EN 1170-7



FM109569 **the Sign of Quality** EMS 73529

O|S|C|R|E|T|E|
construction products



FLOWCAST GRC

High Performance Multi-functional Admixture for GRC

Compatibility

Flowcast GRC is suitable for use with all types of cements and offers a wide range of benefits particularly in the production of free flowing concrete/grout.

Storage

Store the product in a dry environment at temperatures between 5 and 30 degrees centigrade. Moisture ingress will cause the product to harden.

Handling

Flowcast GRC is a non hazardous product but in line with normal handling procedures, protective gloves and goggles should be worn to avoid contact with skin and eyes.

Refer to the Material Safety Data Sheet for full details.

Packaging

Flowcast GRC is available in the following packs: as a loose powdered additive in sealed 15 kg plastic containers and 250 gram plastic sachets supplied in a box containing 56 sachets.

Disclaimer

The physical properties quoted are typical, and should not be taken as a specification. The information supplied in our literature is based on data and experience and is given in good faith. Our policy is one of continuous research and development and we reserve the right to update this information at any time; customers should therefore ensure they have the latest issue. Whilst we guarantee the consistent high quality of our products, we have no control over the circumstances in which our materials are used, site conditions or the execution of the work and are therefore unable to accept any liability for any loss or damage which may arise as a result thereof. Materials are supplied in accordance with our standard conditions of sale.

Batching order and mixing procedure

- 1/ Mix cement and water together to produce high viscosity slurry
- 2/ Add Flowcast and mix to produce low viscosity slurry
- 3/ Add sand whilst mixing
- 4/ Adjust water content (within specification) if necessary to required consistence
- 5/ Slowly mix in fibres

These procedures are a guide and other methods may be employed, however, the admixture MUST be added to WETTED cement and NOT added to the sand, this will negate the effects of the admixture and the plastic and hardened properties will not be achieved.

Call the OSCRETE Technical Department for further information.

OSCRETE is a division of Christeyns UK Ltd.
Rutland Street
Bradford
West Yorkshire
BD4 7EA
United Kingdom

Telephone: +44 (0)1274 393286

Fax: +44 (0)1274 309143

e-mail: info@oscrete.co.uk

Website: www.oscrete.co.uk

PDS 7611 Rev 04 10/01/2014